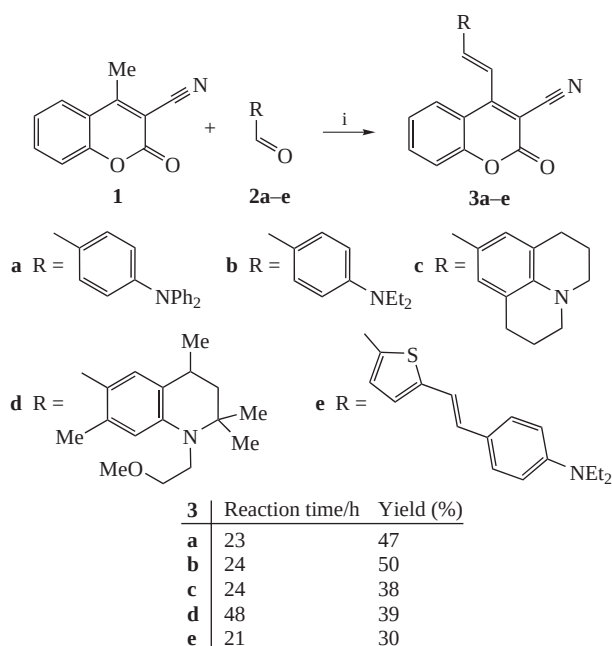


Table 1 The absorption data for the synthesized products **3a–e** in various solvents.

Compound	$\lambda_{\max}/\text{nm}$						$\Delta\lambda_{\max}/\text{nm}^a$	$\epsilon^b/\text{dm}^3 \text{ mol}^{-1} \text{ cm}^{-1}$	$\beta \text{ (a.u.)}^c$
	1,4-dioxane	PhCl	CH_2Cl_2	Me_2CO	MeCN	EtOH			
$E_T(30)^d$	36	36.8	40.7	42.2	45.6	51.9	–	–	–
3a	466	488	490	468	470	489	24	15660	19303.3
3b	486	508	518	501	506	523	37	9261	15598.9
3c	518	549	560	548	545	568	50	5792	15097.7
3d	506	534	540	524	527	548	42	15140	8434.2
3e	529	560	560	535	574	559	45	15698	54453.0

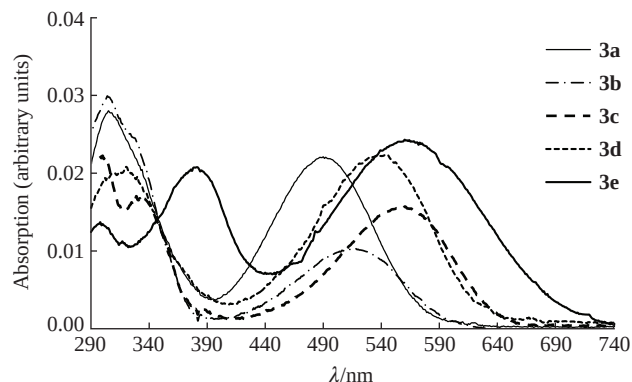
^a $\Delta\lambda_{\max}$ is the maximum difference between absorption maxima in different solvents. ^b ϵ is the molar extinction calculated for 1,4-dioxane solution. ^c β is the first hyperpolarizability. ^d $E_T(30)$ is the empirical parameter of solvent polarity (kcal mol^{-1}).²⁷

**Scheme 1** Reagents and conditions: i, MeCN, piperidine, reflux.

All products were characterized by ^1H and ^{13}C NMR as well as HRMS methods. Optical properties of compounds **3a–e** are summarized in Figure 1 and Table 1.

With the solvents varying from slightly polar 1,4-dioxane to moderately polar dichloromethane, a shift of 24–42 nm of the absorption maxima to longer wavelength has been observed for all the chromophores **3a–e**.

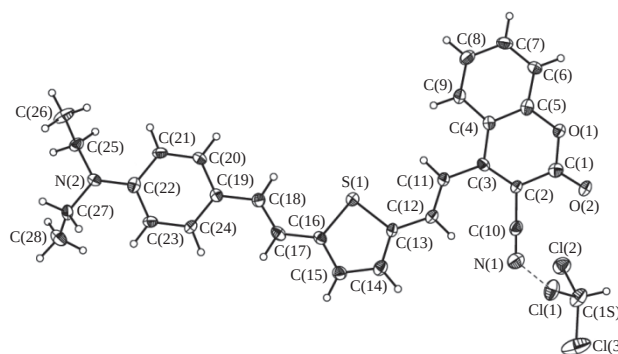
In a series from weakly or moderately polar solvents to highly polar ones, a negative solvatochromism was observed. With increasing polarity in a group of highly polar solvents, namely acetone, acetonitrile and ethanol, a linear relationship occurs for

**Figure 1** The absorption spectra of the synthesized products **3a–e**, $C = 0.003 \text{ mg ml}^{-1}$.

compounds **3a**, **3b** and **3d**. Interestingly, the absorption maximum in acetonitrile for compound **3e** is in a longer wavelength range, compared with the absorption maximum in ethanol, which is accounted for by the formation of specific solvate forms.

The structure of compound **3e** was confirmed by XRD (Figure 2).[‡] It crystallizes as solvate with chloroform in the centrosymmetric space group $P2_1/n$. The molecule **3e** is almost planar with maximum deviation from planarity due to rotation around the C(3)–C(11) bond, with torsion angle C(2)–C(3)–C(11)–C(12) being 18.7° . In the crystal, the cyano group of compound **3e** participates in the shortened $\text{N}\cdots\text{Cl}$ interactions with the chloroform molecule: N–Cl distance is 2.99–3.07 Å and N–Cl–C angle is $159\text{--}167^\circ$, which can be considered as the halogen bond. In addition, the molecules participate in a strong stacking interaction between the 2-oxo-2H-chromene-3-carbonitrile rings, with the shortest C $\cdots$ C contact being 3.37 Å.

Considering the pronounced solvatochromism of compounds **3a–e**, it is reasonable to suppose that these molecules can be characterized by high values of first hyperpolarizability β for the thermal ellipsoids at $p = 50\%$. For all the molecules we performed the geometry optimization without symmetry restriction using the density functional theory with PBE0 approximation and def-2-TZVP basis set. The calculations of β were carried out

**Figure 2** Molecular structure of compound **3e**.

[‡] Crystal data for **3e**. $\text{C}_{29}\text{H}_{25}\text{Cl}_3\text{N}_2\text{O}_2\text{S}$, monoclinic, space group $P2_1/n$, at 120(2) K: $a = 9.511(3)$, $b = 7.209(2)$ and $c = 39.548(12)$ Å, $\beta = 90.018(6)^\circ$, $V = 2711.8(15)$ Å³, $Z = 4$, $Z' = 1$, $d_{\text{calc}} = 1.401 \text{ g cm}^{-3}$. Intensities of 30208 reflections were measured using Bruker APEX-II CCD [$\lambda(\text{MoK}\alpha) = 0.71072$ Å], $2\theta < 55^\circ$ and 6252 independent reflections were used in the further refinement. The structure was solved by direct method and refined by the full-matrix least-squares technique against F^2 in the anisotropic–isotropic approximation. The refinement converged to $wR_2 = 0.1755$ and $\text{GOF} = 0.877$ for all independent reflections [$R_1 = 0.0691$ was calculated against F for 2507 observed reflections with $I > 2\sigma(I)$]. All calculations were performed using SHELXTL-2014/6.

CCDC 1874236 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via <http://www.ccdc.cam.ac.uk>.

using M05-2X/6-31+G(d) approximation that had been shown to be the appropriate method.^{28–31}

The β values were calculated by the numerical second derivative of electric dipole moment with respect to the applied field, as implemented into the Gaussian 09 program. For all molecules **3a–e**, the nature of the emission band was estimated by means of TD-DFT calculation with application of the conductor-like polarization continuum model CPCM³² of acetonitrile solvent. The TD-DFT calculations have revealed that the lowest energy transitions S1 $\rightarrow$ S0 are mainly HOMO to LUMO, which corresponds to the transition from the donor part, designated as R in Scheme 1, to the acceptor one, namely the 2-oxo-2H-chromene-3-carbonitrile ring. The β values are significantly higher than those for the family of stilbene derivatives or their thiophene analogues.^{33–35} Compound **3e** has the highest β value equal to 54453.0 a.u., which is only slightly lower than that for 2-dicyanomethylidene-3-cyano-4-{2E-[2-(2E-{4-[di(2-acetoxyethyl)-amino]phenyl}vinyl)-3,4-dibutylthien-5-yl]vinyl}-5,5-dimethyl-2,5-dihydrofuran (FTC).^{36,37} Thus, we can propose that the synthesized compounds can be promising for the design of NLO materials.

In summary, a series of new 2-oxo-4-vinyl-2H-chromene-3-carbonitrile derivatives were synthesized by the Knoevenagel reaction of 4-methyl-2-oxo-2H-chromene-3-carbonitrile with aromatic and heteroaromatic aldehydes. The first hyperpolarizability β of the obtained compounds was calculated using M05-2X functional and 6-31+G(d) basis set. Optical properties and solvatochromism in solvents of various polarity, namely 1,4-dioxane, chlorobenzene, dichloromethane, acetonitrile and ethanol, were explored. The new class of dyes may be useful for NLO devices and other applications.

This work was supported by the Russian Science Foundation (project no. 17-73-10433). The X-ray diffraction data were obtained using the equipment of Center for Molecules Composition Studies of INEOS, RAS. DFT calculations were supported by the Russian Foundation for Basic Research (grant no. 18-33-20075).

Online Supplementary Materials

Supplementary data associated with this article can be found in the online version at doi: 10.1016/j.mencom.2019.05.020.

References

- J. Liu, G. Xu, F. Liu, I. Kityk, X. Liu and Z. Zhen, *RSC Adv.*, 2015, **5**, 15784.
- W. Wu, J. Qin and Z. Li, *Polymer*, 2013, **54**, 4351.
- Z. Shi, J. Luo, S. Huang, B. M. Polishak, X.-H. Zhou, S. Liff, T. R. Younkin, B. A. Block and A. K.-Y. Jen, *J. Mater. Chem.*, 2012, **22**, 951.
- L. R. Dalton, A. W. Harper, R. Ghosn, W. H. Steier, M. Ziari, H. Fetterman, Y. Shi, R. V. Mustacich, A. K.-Y. Jen and K. J. Shea, *Chem. Mater.*, 1995, **7**, 1060.
- C. Zhang, L. R. Dalton, M.-C. Oh, H. Zhang and W. H. Steier, *Chem. Mater.*, 2001, **13**, 3043.
- C. Peng, J. Wu, J. Liu, L. Qiu, X. Liu, S. Bo and Z. Zhen, *Polym. Chem.*, 2013, **4**, 2703.
- K. Yu. Suponitsky, T. V. Timofeeva and M. Yu. Antipin, *Russ. Chem. Rev.*, 2006, **75**, 457 (*Usp. Khim.*, 2006, **75**, 515).
- Y. Shi, D. Frattarelli, N. Watanabe, A. Facchetti, E. Cariati, S. Righetto, E. Tordin, C. Zuccaccia, A. Macchioni, S. L. Wegener, C. L. Stern, M. A. Ratner and T. J. Marks, *J. Am. Chem. Soc.*, 2015, **137**, 12521.
- D. Briers, L. De Cremer, G. Koegelberghs, S. Foerier, T. Verbiest and C. Samyn, *Macromol. Rapid Commun.*, 2007, **28**, 942.
- Y. V. Pereverzev, K. N. Gunnerson, O. V. Prezhdo, P. A. Sullivan, Y. Liao, B. C. Olbricht, A. J. P. Akelaitis, A. K.-Y. Jen and L. R. Dalton, *J. Phys. Chem. C*, 2008, **112**, 4355.
- M. J. Cho, J. H. Lim, C. S. Hong, J. H. Kim, H. S. Lee and D. H. Choi, *Dyes Pigm.*, 2008, **79**, 193.
- A. Kaneko, M. Tsukase and M. Satou, *US Patent 9798044B2*, 2017.
- D. Huang and B. Chen, *US Patent 6750603B2*, 2004.
- A. I. Tolmachev, A. D. Kachkovskii, M. A. Kudanova, V. V. Kurdiukov, S. Ksenzov and S. Schrader, *Dyes Pigm.*, 2007, **74**, 348.
- K. A. Chudov, K. S. Levchenko, N. O. Poroshin, E. V. Zinoviev, G. E. Adamov, P. S. Shmelin and E. P. Grebennikov, *XII Russian Conference 'Technologies and Materials for Extreme Conditions (Laser Technologies, Electric Current Sources and Materials)'*, Tuapse, 2017, p. 227.
- K. S. Levchenko, K. A. Chudov, N. O. Poroshin, E. V. Zinoviev, P. A. Chicheva, E. A. Shohina, P. S. Shmelin and E. P. Grebennikov, *VII International Conference on Photonics and Information Optics*, Moscow, 2018, p. 138.
- A. Y. Bochkov, I. O. Akchurin, O. A. Dyachenko and V. F. Traven, *Chem. Commun.*, 2013, **49**, 11653.
- I. O. Akchurin, A. I. Yakhutina, A. Y. Bochkov, N. P. Solovjova, M. G. Medvedev and V. F. Traven, *J. Mol. Struct.*, 2018, **1160**, 215.
- A. Sharma, *International Journal of Environmental Science: Development and Monitoring (IJESDM)*, 2013, **4**, special issue 3, 12.
- G. A. Reynolds and K. H. Drexhage, *Opt. Commun.*, 1975, **13**, 222.
- K. Hara, T. Sato, R. Katoh, A. Furube, Y. Ohga, A. Shinpo, S. Suga, K. Sayama, H. Sugihara and H. Arakawa, *J. Phys. Chem. B*, 2003, **107**, 597.
- Q. Chen, N. Wu, Y. Liu, X. Li and B. Liu, *RSC Adv.*, 2016, **6**, 87969.
- F. Al-Omran, M. M. A. Khalik, H. Al-Awadhi and M. H. Elnagdi, *Tetrahedron*, 1996, **52**, 11915.
- M. H. Elnagdi, N. A. Al-Awadi, A. Kumar and M. A. Khalik, *Heteroat. Chem.*, 2001, **12**, 47.
- K. S. Levchenko, K. A. Chudov, E. V. Zinoviev, K. A. Lyssenko, D. U. Demin, N. O. Poroshin, P. S. Shmelin and E. P. Grebennikov, *Tetrahedron Lett.*, 2018, **59**, 2788.
- F. Liu, H. Xiao, Y. Yang, H. Wang, H. Zhang, J. Liu, S. Bo, Z. Zhen, X. Liu and L. Qiu, *Dyes Pigm.*, 2016, **130**, 138.
- C. Reichardt, *Chem. Rev.*, 1994, **94**, 2319.
- K. Yu. Suponitsky, S. Tafur and A. E. Masunov, *J. Chem. Phys.*, 2008, **129**, 044109.
- K. Yu. Suponitsky, Y. Liao and A. E. Masunov, *J. Phys. Chem. A*, 2009, **113**, 10994.
- K. Yu. Suponitsky and A. E. Masunov, *J. Chem. Phys.*, 2013, **139**, 094310.
- K. Yu. Suponitsky, A. E. Masunov and M. Yu. Antipin, *Mendeleev Commun.*, 2009, **19**, 311.
- M. Cossi and V. Barone, *J. Chem. Phys.*, 2001, **115**, 4708.
- V. P. Rao, A. K. Y. Jen, K.-Y. Wong, K. J. Drost and R. M. Mininni, *Proc. SPIE*, 1992, **1775**, 32.
- K. Clays and A. Persoons, *Phys. Rev. Lett.*, 1991, **66**, 2980.
- K. Clays and A. Persoons, *Rev. Sci. Instrum.*, 1992, **63**, 3285.
- T. Kinnibrugh, S. Bhattacharjee, P. Sullivan, C. Isborn, B. H. Robinson and B. E. Eichinger, *J. Phys. Chem. B*, 2006, **110**, 13512.
- K. Yu. Suponitsky, A. E. Masunov and M. Yu. Antipin, *Mendeleev Commun.*, 2008, **18**, 265.

Received: 10th December 2018; Com. 18/5767