

Synthesis and optical properties of novel unsymmetrically substituted benzothiadiazole-based luminophores

Pavel S. Gribov,^a Dmitry A. Lypenko,^b Artem V. Dmitriev,^b Sergey I. Pozin,^b
Maxim A. Topchiy,^c Andrey F. Asachenko,^c Dmitry A. Loginov^{a,d} and Sergey N. Osipov^{a,e}

^a A. N. Nesmeyanov Institute of Organoelement Compounds, Russian Academy of Sciences, 119991 Moscow, Russian Federation. E-mail: osipov@ineos.ac.ru

^b A. N. Frumkin Institute of Physical Chemistry and Electrochemistry, Russian Academy of Sciences, 199071 Moscow, Russian Federation


^c A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, 119991 Moscow, Russian Federation

^d G. V. Plekhanov Russian University of Economics, 117997 Moscow, Russian Federation

^e Moscow Region State University, 141014 Mytishchi, Moscow Region, Russian Federation

DOI: 10.1016/j.mencom.2021.01.009


New unsymmetrically substituted benzothiadiazoles were synthesized from 4,7-dibromo-2,1,3-benzothiadiazole via the sequence of Pd-catalyzed Suzuki and Buchwald–Hartwig cross-coupling reactions with 4-methoxyphenylboronic acid and heterocyclic amines, respectively. Based on initially performed photophysical study as well as DFT calculation, these compounds, in particular with dibenzoazepine core, can be selected as promising scaffolds for further fine-tuning of their properties to be used in optoelectronics including OLED technologies.

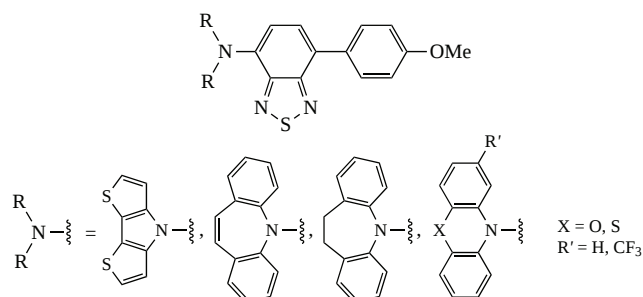

Keywords: benzothiadiazoles, luminophores, cross-coupling, synthesis, photophysical properties.

During the past decade, 4,7-disubstituted 2,1,3-benzothiadiazole (BTD) derivatives with extended π -conjugation owing to their outstanding electron affinity,¹ carrier transport abilities, thermal and chemical stabilities have been extensively studied as privileged scaffolds for the construction of different optoelectronic devices, *e.g.*, organic light emitting diodes (OLEDs),² field effect transistors (OFETs),³ solar cells (OSCs),⁴ bioprobes,⁵ and chemosensors.⁶ Despite prominent advances highlighting the great potential of these compounds, particularly attention is focused on direct substitution at the 4,7-positions with amino groups to afford unsymmetrical BTDs of donor–acceptor type. The most promising examples of such molecules were designed for dye-sensitized solar cells with an apparent increase in the power conversion efficiency⁷ and for thermally activated delayed fluorescence (TADF) emitters with high external quantum efficiency.⁸ Taking into account the fact that electronic and steric nature of substituents at positions 4 or/and 7 can dramatically affect performance and photophysical properties of the target molecules, herein we report on the synthesis of a series of novel unequally substituted BTD derivatives with phenoxazine, phenothiazine, dithienopyrrole and dibenzazepine as electron donor units as well as our initial investigation on their photophysical characteristics to estimate a potential application of these compounds in materials science.

A synthetic route from commercially available 4,7-dibromo-2,1,3-benzothiadiazole **1** (Scheme 1) to the amino BTDs **3a–f** included a sequence of two Pd-catalyzed cross-coupling reactions. The first step, Suzuki mono-coupling of dibromide **1** with 4-methoxyphenylboronic acid, was accomplished by slightly

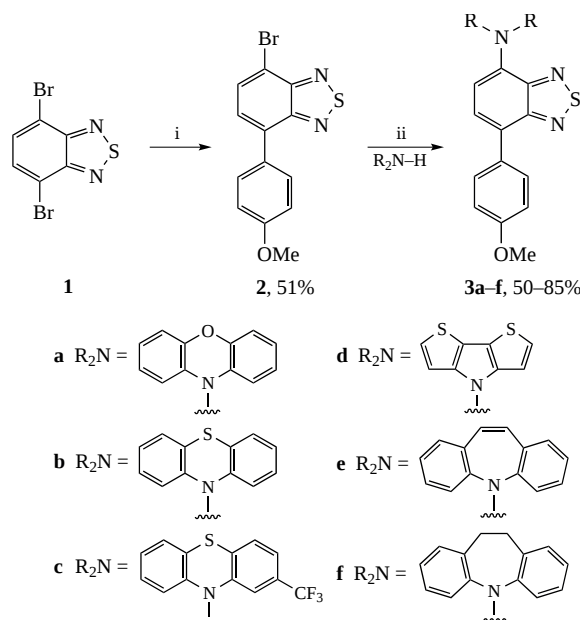

Scheme 1 Reagents and conditions: i, 4-MeOC₆H₄B(OH)₂ (1 equiv.), NaHCO₃ (3 equiv.), 1,4-dioxane/water (3:1), Pd(PPh₃)₂Cl₂ (1 mol%), reflux, 24 h; ii, R₂N–H (1.05 equiv.), Pd(OAc)₂ (5 mol%), RuPhos (10 mol%), Bu^tONa (1.5 equiv.), 1,4-dioxane, 100 °C, 24 h.

modified procedure previously described for selective formation of monobromide **2**⁹ under catalysis with significantly reduced

Table 1 Photophysical properties of compounds **3a–f**.

Compound	$\lambda_{\text{max}}^{\text{abs}}/\text{nm}$	$\lambda_{\text{max}}^{\text{PL}}/\text{nm}$	$\phi_{\text{PL}} (\%)$
3a	383	480	0.2
3b	384	540	0.1
3c	385	530	0.5–1
3d	437	542	2–3
3e	455	587	26–33
3f	467	591	32–40

amount of Pd-complex. For the next Buchwald–Hartwig coupling of compound **2** with selected cyclic amines, the combination of 5 mol% Pd(OAc)₂, 10 mol% RuPhos (2-dicyclohexylphosphino-2',6'-diisopropoxybiphenyl) and 1.5 equiv. Bu^tONa has proved to be the most effective catalytic system among tested.

All compounds **3a–f** were isolated by flash chromatography on silica gel and additionally purified by sublimation (200–220 °C/0.1 Torr). Their structures were proved by ¹H NMR, ¹³C NMR and HRMS (see Online Supplementary Materials).

Photoluminescent properties of compounds **3a–f** are summarized in Table 1. The optical spectra were recorded for nonde-aerated 0.2–20 μM solutions in toluene at room temperature (see Online Supplementary Materials, Figures S1–S6). The fluorescence quantum yield was estimated by Parker–Rees method. Rhodamine B in ethanol solution (Q = 65–70%) was chosen as a standard.¹⁰

All compounds exhibit intense absorption bands at 383–467 nm and fluorescence emission in the green-yellow region (480–591 nm). Figure 1 shows the absorption and emission spectra for compound **3f**. Surprisingly, the phenoxazine, phenothiazine and dithienopyrrole derivatives **3a–d** showed very low quantum yields (0.1–3%). In contrast, the benzoazepine compounds **3e,f** have rather high fluorescence efficiency, with the best quantum yield being 40% for **3f**.

To make spectral assignments, we calculated the electronic absorption spectra and the frontier molecular orbitals using the TD-DFT method at the B3LYP/DZP level. Earlier we showed that B3LYP is the best exchange correlation functional for estimation of the differences in energy between the frontier orbitals of organic dyes.¹¹ The calculated absorption bands for all studied compounds are only 10–40 nm differ relative to experimental values (Table 2). In the case of the dibenzoazepine (**3e**) and dihydrodibenzoazepine (**3f**) derivatives, the most intense absorption band corresponds to the $\pi \rightarrow \pi^*$ transition, which is formed by HOMO $\rightarrow$ LUMO orbitals. Both these frontier orbitals are mainly located at the benzothiadiazole moiety (see Online Supplementary Materials, Figure S7). In contrast, in the case of phenoxazine (**3a**) and phenothiazine (**3b,c**) compounds, HOMO is located at the phenoxazine and phenothiazine fragments, while

Table 2 General analysis of the absorption bands by TD DFT calculations at the B3LYP/DZP level.

Compound	Experimental absorption maxima/nm	Calculated absorption maxima/nm	Calculated oscillator strengths	Main MOs responsible for excitation ^a
3a	383	413 665	0.179106 0.000579	HOMO–1 $\rightarrow$ LUMO (99%) HOMO $\rightarrow$ LUMO (99%)
3b	384	408 571	0.185355 0.004237	HOMO–1 $\rightarrow$ LUMO (99%) HOMO $\rightarrow$ LUMO (99%)
3c	385	413 549	0.191621 0.007352	HOMO–1 $\rightarrow$ LUMO (99%) HOMO $\rightarrow$ LUMO (99%)
3d	437	399 479 528	0.070450 0.141245 0.000678	HOMO–2 $\rightarrow$ LUMO (99%) HOMO–1 $\rightarrow$ LUMO (99%) HOMO $\rightarrow$ LUMO (100%)
3e	455	403 446	0.003554 0.15404	HOMO $\rightarrow$ LUMO + 1 (98%) HOMO $\rightarrow$ LUMO (98%)
3f	467	334 450	0.004909 0.16546	HOMO–1 $\rightarrow$ LUMO (99%) HOMO $\rightarrow$ LUMO (98%)

^a Values in parentheses give the percentage contribution of the corresponding orbitals to the total transition.

LUMO remains at the benzothiadiazole. However, the band corresponding to this charge transfer transition has very low intensity because of the absence of conjugation between cyclic moieties in these compounds (for example, the dihedral angle phenoxazine/benzothiadiazole in molecule of **3a** is 86.4°). Therefore, for compounds **3a,b** the most intense absorption band is provided by HOMO–1 $\rightarrow$ LUMO transition, where the HOMO–1 orbital is mainly located at benzothiadiazole and 4-methoxyphenyl substituent. The introduction of the CF₃ group into the phenothiazine moiety leads only to a slight bathochromic shift of the most intense band and the increase of the HOMO–LUMO gap by 0.08 eV. Dithienopyrrole derivative **3d** exhibits closely related photophysical behavior involving HOMO–1 and HOMO–2 to the main transitions instead of HOMO.

Noteworthy, according to DFT calculations, the heterocyclic moieties in all studied compounds are not coplanar that prevents its conjugation. It can be explained by the sterical hindrance between these moieties due to its bulkiness and close proximity. We propose that the addition of acetylene or phenyl spacer between them should prominently improve photophysical properties of the final compounds.

In conclusion, an efficient scheme for the preparation of a series of new unsymmetrically substituted benzothiadiazoles has been elaborated *via* sequence of two Pd-catalyzed cross coupling Suzuki and Buchwald–Hartwig reactions. Based on our results, these compounds, in particular with dibenzoazepine core, can be selected as promising scaffolds for further fine-tuning of their properties to be used in optoelectronics including OLED technologies.

This work was supported by the Russian Foundation for Basic Research (grant no. 19-29-08038). NMR studies and spectral characterization were performed with the financial support from the Ministry of Science and Higher Education of the Russian Federation using the equipment of the Center for Molecular Composition Studies of INEOS RAS. Part of this work was carried out by M. A. Topchiy and A. F. Asachenko within the framework of the State Program of A. V. Topchiev Institute of Petrochemical Synthesis of the Russian Academy of Sciences.

Online Supplementary Materials

Supplementary data associated with this article can be found in the online version at doi: 10.1016/j.mencom.2021.01.009.

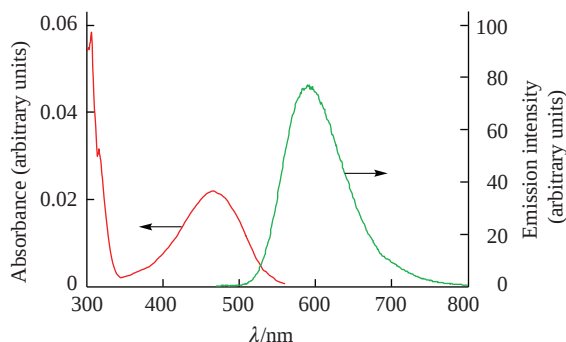


Figure 1 The absorption and emission spectra of compound **3f** in toluene ($C = 0.2 \times 10^{-5}$ M, $\lambda_{\text{ex}} = 460$ nm, 20 °C).

References

- 1 T. S. Sukhikh, D. S. Ogienko, D. A. Bashirov and S. N. Konchenkova, *Russ. Chem. Bull., Int. Ed.*, 2019, **68**, 651 (*Izv. Akad. Nauk, Ser. Khim.*, 2019, 651).
- 2 C. D. Müller, A. Falcou, N. Reckefuss, M. Rojahn, V. Wiederhirn, P. Rudati, H. Frohne, O. Nuyken, H. Becker and K. Meerholz, *Nature*, 2003, **421**, 829.
- 3 (a) H. N. Tsao, D. M. Cho, I. Park, M. R. Hansen, A. Mavrinskiy, D. Y. Yoon, R. Graf, W. Pisula, H. W. Spiess and K. Müllen, *J. Am. Chem. Soc.*, 2011, **133**, 2605; (b) M. Zhang, H. N. Tsao, W. Pisula, C. Yang, A. K. Mishra and K. Müllen, *J. Am. Chem. Soc.*, 2007, **129**, 3472; (c) P. Sonar, S. P. Singh, Y. Li, M. S. Soh and A. Dodabalapur, *Adv. Mater.*, 2010, **22**, 5409.
- 4 (a) Y. Li, *Acc. Chem. Res.*, 2012, **45**, 723; (b) J. Du, M. C. Biewer and M. C. Stefan, *J. Mater. Chem. A*, 2016, **4**, 15771; (c) Q. Liu, H. Zhan, C.-L. Ho, F.-R. Dai, Y. Fu, Z. Xie, L. Wang, J.-H. Li, F. Yan, S.-P. Huang and W.-Y. Wong, *Chem. – Asian J.*, 2013, **8**, 1892.
- 5 (a) B. A. D. Neto, P. H. P. R. Carvalho and J. R. Correa, *Acc. Chem. Res.*, 2015, **48**, 1560; (b) P. H. Carvalho, J. R. Correa, B. C. Guido, C. C. Gatto, H. C. B. De Oliveira, T. A. Soares and B. A. D. Neto, *Chem. – Eur. J.*, 2014, **20**, 15360.
- 6 J. Wu, G. Lai, Z. Li, Y. Lu, T. Leng, Y. Shen and C. Wang, *Dyes Pigm.*, 2016, **124**, 268.
- 7 M. Kimura, M. Karasawa, N. Sasagawa, K. Takemoto, R. Goto and S. Mori, *Chem. Lett.*, 2012, **41**, 1613.
- 8 F. Ni, Z. Wu, Z. Zhu, T. Chen, K. Wu, C. Zhong, K. An, D. Wei, D. Ma and C. Yang, *J. Mater. Chem. C*, 2017, **5**, 1363.
- 9 (a) Z. Peng, Z. Wang, Z. Huang, S. Liu, P. Lu and Y. Wang, *J. Mater. Chem. C*, 2018, **6**, 7864; (b) A. A. Vasil'ev, M. I. Struchkova, A. B. Sheremetev, F. S. Levinson, R. V. Varganov and K. A. Lyssenko, *Russ. Chem. Bull., Int. Ed.*, 2011, **60**, 2306 (*Izv. Akad. Nauk, Ser. Khim.*, 2011, 2262).
- 10 (a) F. L. Arbeloa, P. R. Ojeda and I. L. Arbeloa, *J. Lumin.*, 1989, **44**, 105; (b) T. Karstens and K. Kobs, *J. Phys. Chem.*, 1980, **84**, 1871.
- 11 (a) A. P. Molotkov, M. A. Arsenov, D. A. Kapustin, D. V. Muratov, N. E. Shepel', Y. V. Fedorov, A. F. Smol'yakov, E. I. Knyazeva, D. A. Lypenko, A. V. Dmitriev, A. E. Aleksandrov, E. I. Maltsev and D. A. Loginov, *ChemPlusChem*, 2020, **85**, 334; (b) V. B. Kharitonov, Y. V. Nelyubina, D. V. Muratov, N. E. Shepel and D. A. Loginov, *J. Organomet. Chem.*, 2020, **911**, 121154.

Received: 17th September 2020; Com. 20/6314