

Effects of Sn^{4+} dopant ions located either in the bulk or at crystallite surfaces on the ultraviolet photocatalytic activity of anatase


Mikhail V. Korolenko, Pavel B. Fabritchnyi* and Mikhail I. Afanasov

Department of Chemistry, M. V. Lomonosov Moscow State University, 119991 Moscow, Russian Federation.

Fax: +7 495 932 8846; e-mail: pf@radio.chem.msu.ru

DOI: 10.1016/j.mencom.2021.07.045

Isovalent Sn^{4+} dopant cations do not have a significant effect on the ultraviolet photocatalytic activity of anatase (TiO_2) regardless of their location in the bulk or at the surfaces of crystallites. This is due to the formation of no charge balance oxygen vacancies V_O acting as (e^-, h^+) recombination centers towards photogenerated electrons and holes upon doping with Sn^{4+} . Nevertheless, the analysis of a sample containing surface-located heterovalent Sb^{3+} ions (isoelectronic with Sn^{2+}) revealed a significant weakening of the negative effect of V_O , which can be accounted for by the presence of a stereochemically active lone pair E of 5s electrons in the nearest vicinity of V_O .

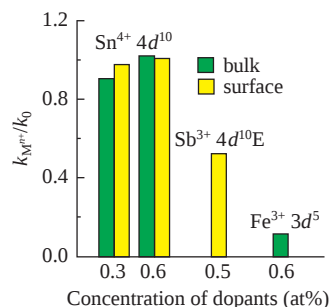

Keywords: Sn^{4+} -doped anatase TiO_2 , bulk and surface sites, photocatalytic activity, decolorization of methyl orange, ^{119}Sn and ^{121}Sb Mössbauer spectroscopy, stereochemically active lone pair.

Earlier, we used ^{119}Sn Mössbauer spectroscopy¹ to study the stabilization of tin dopant ions at uppermost surface layers of anatase crystallites and physicochemical processes occurring at the $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ /gas interface. The samples were synthesized by the hydrogen annealing of polycrystalline $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ obtained by the calcination of coprecipitated Ti^{IV} and Sn^{IV} hydroxides in air. Upon annealing, Sn^{4+} ions on crystallite surfaces were reduced to a divalent state and, owing to their stereochemically active electronic lone pair E, located on low coordination sites ($\text{CN} < 6$) energetically unfavorable for Ti^{4+} . The subsequent contact with ambient air resulted in the formation of isolated Sn^{4+} impurity centers, whose surface location was confirmed by both X-ray photoelectron spectroscopy (XPS) and an analysis of ^{119}Sn Mössbauer spectra recorded after exposure of H_2 -annealed $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ to various gases.¹ These $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ powders are particularly suitable for comparing the effects of a dopant located at surface sites or in the bulk of TiO_2 -based photocatalytic materials promising for solar energy conversion.^{2–4} The advantage provided by the use of Sn^{4+} dopant ion, which is isovalent with the host Ti^{4+} , is due to the fact that its presence in TiO_2 does not involve the formation of interfering charge-balance defects, in contrast to heterovalent additive ions.⁵ Moreover, the investigation of $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ may provide some insight into the effects related to intermediately

formed Sn^{2+} ions. Thus, we studied the photocatalytic activity of $\text{Ti}_{1-x}\text{Sn}_x\text{O}_2$ powders in the decolorization reaction of methyl orange (MO), which was recently used⁶ to compare the modifying actions of bulk-located Cr^{3+} and Fe^{3+} .

The single-phase anatase TiO_2 powders were irradiated using a LED ($\lambda = 370$ nm, $P = 3$ W). Optical density was determined at $\lambda = 460$ nm, and the values of k were calculated using a linear equation of first-order reactions.

Samples containing Sn^{4+} ions located in the bulk of crystallites were obtained by the annealing of a coprecipitated $\text{Ti}_{1-x}\text{Sn}_x(\text{OH})_4$ precursor ($x = 0.003$ or 0.006) in air at 500°C for 2 h. To obtain the samples containing Sn^{4+} at surface sites, the same precursor was annealed in a hydrogen atmosphere at 500°C for 2 h. To prepare the hydroxide precursors $\text{Ti}_{1-x}\text{Sn}_x(\text{OH})_4$, a stannic chloride solution enriched in the Mössbauer isotope ^{119}Sn to 92% was used. Figure 1(a) shows the Mössbauer spectrum of the air-annealed sample (material 1, see Online Supplementary Materials). The spectral parameters (the isomer shift $\delta_1 = 0.01 \pm 0.01$ mm s^{−1}, the quadrupole splitting $\Delta E_{Q1} = 0.41 \pm 0.01$ mm s^{−1}, the full width at half maximum of each doublet component $\Gamma_1 = 0.88$ mm s^{−1}, and the spectral contribution $A_1 = 100\%$) evidenced the presence of tetravalent tin on a site of unique type assignable to a distorted oxygen octahedron of the anatase structure. Moreover, the above

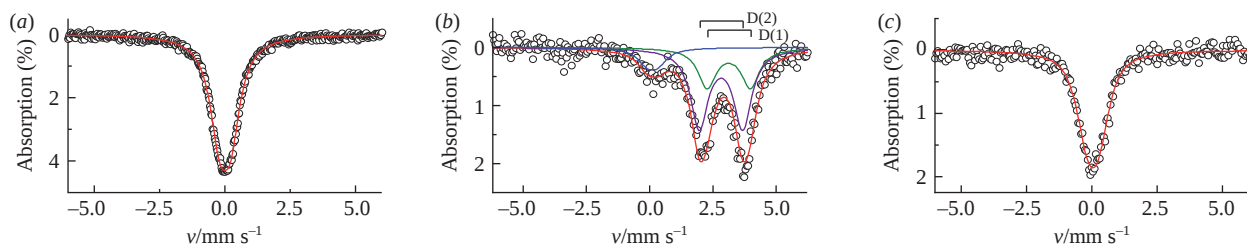


Figure 1 ^{119}Sn Mössbauer spectra (recorded at 100 K) of 0.6 at% Sn/TiO_2 samples obtained by the annealing of a coprecipitated precursor (a) in air (2 h at 500°C) and (b) in H_2 (2 h at 400°C , *in situ* measurements) and (c) after exposure of the hydrogen-annealed sample to ambient air.

values are consistent with those reported earlier for a similar sample annealed in air at 650 °C, which were ascribed to the bulk-located Sn^{4+} . To determine the valence state of tin upon the hydrogen annealing of $\text{Ti}_{1-x}\text{Sn}_x(\text{OH})_4$ (hydrogen-annealed material 2, see Online Supplementary Materials), we performed *in situ* Mössbauer measurements at 100 K in the reactor used for hydrogen annealing, which was equipped with a lateral thin-window quartz sample cell to avoid the contact of a test sample with ambient air [Figure 1(b)]. As can be seen, the majority of the Sn^{4+} was reduced to a divalent state, revealed by the appearance of an asymmetric doublet at positive Doppler velocities. This new spectral component is a superposition of two quadrupole doublets D1 and D2, either being imputable to Sn^{II} species possessing a lone pair E but located at nonequivalent sites with $\text{CN} < 6$. Their spectral parameters are $\delta_{2(1)} = 3.18 \pm 0.04 \text{ mm s}^{-1}$, $\Delta E_{\text{Q}2(1)} = 1.71 \pm 0.11 \text{ mm s}^{-1}$, $\Gamma_{2(1)} = 0.85 \pm 0.03 \text{ mm s}^{-1}$, and $A_{2(1)} = 30\%$; $\delta_{2(2)} = 2.82 \pm 0.04 \text{ mm s}^{-1}$, $\Delta E_{\text{Q}2(2)} = 1.72 \pm 0.11 \text{ mm s}^{-1}$, $\Gamma_{2(2)} = 0.85 \pm 0.03 \text{ mm s}^{-1}$, and $A_{2(2)} = 59\%$. They are consistent with those previously assigned to Sn^{2+} ions on the surfaces of anatase TiO_2 crystallites.¹ As for the minor third spectral component, its parameters ($\delta_{\text{m}} = 0.07 \pm 0.05 \text{ mm s}^{-1}$, $\Delta E_{\text{Qm}} = 0.44 \pm 0.13 \text{ mm s}^{-1}$, $\Gamma_{\text{m}} = 0.85 \pm 0.03 \text{ mm s}^{-1}$, and $A_{\text{m}} = 11\%$) are assignable to pristine Sn^{4+} ions still remaining in the bulk positions.

Figure 1(c) shows the ^{119}Sn Mössbauer spectrum recorded after contact of material 2 cooled to room temperature with ambient air. This spectrum revealed the reoxidation of Sn^{2+} ions and, consequently, their easy accessibility to oxygen molecules, as expected for a surface-located species (material 3, see Online Supplementary Materials). Thus, we used materials 1 (bulk) and 3 (surface) to compare the photocatalytic activities of anatase containing Sn^{4+} in the bulk and on surface sites. The subsequent photocatalytic experiments were carried out at the concentrations $[\text{Sn}]$ of 0.3 and 0.6 at% for both materials 1 and 3. The former value corresponds to the highest concentration of tin utilized in ref. 1 while the latter is the lowest concentration of antimony, still allowing to determine its virtual valence state by means of ^{121}Sb Mössbauer spectroscopy. Figure 2 shows that, in both cases, the location of Sn^{4+} ions did not significantly affect the kinetics, in contrast to a drastic decrease in the activity of the sample doped with Fe^{3+} ions proven to create V_{O} . Thus, it would be tempting to consider the kinetics in the presence of TiO_2 doped with surface-located Sn^{2+} ions exhibiting a positive charge deficiency like Fe^{3+} . Unfortunately, this could not be done because of their fast oxidation under ambient air. For this reason, we studied the kinetics in the presence of TiO_2 powders doped with surface-located Sb^{3+} ions, which possess a lone pair E like Sn^{2+} and are stable in air at room temperature. A sample containing ~0.6 at% Sb^{3+} was prepared using a published procedure⁷ involving dropwise deposition of a SbCl_5 solution on a TiO_2 powder wetted with an ammonia solution. The relevant ^{121}Sb Mössbauer

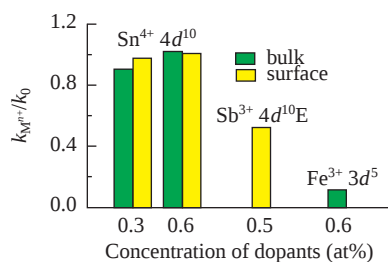


Figure 2 Kinetics of the ultraviolet photocatalytic decolorization of MO in the presence of TiO_2 powder containing Sn^{4+} dopant ions in the bulk or on the surface of crystallites (k_0 is the rate constant in the presence of undoped TiO_2). For comparison, the results obtained for a sample containing ~0.5 at% surface-located Sb^{3+} along with the earlier reported data for a TiO_2 sample containing 0.6 at% Fe^{3+} in the bulk of crystallites are also shown.

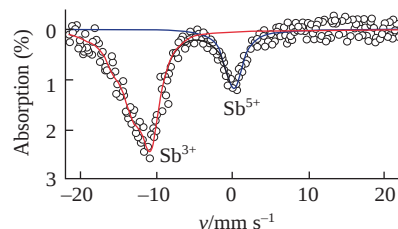


Figure 3 ^{121}Sb Mössbauer spectrum of the hydrogen-annealed 0.6 at% $\text{Sb}^{5+}/\text{TiO}_2$ sample recorded at 100 K.

spectrum (Figure 3) evidenced that the majority of Sb^{5+} ions ($\delta^* = -0.01 \pm 0.1 \text{ mm s}^{-1}$, the quadrupole coupling constant $e^2qQ_{5/2}^* = 2 \pm 2 \text{ mm s}^{-1}$, $\Gamma^* = 2.55 \pm 0.15 \text{ mm s}^{-1}$, and $A^* = 22\%$) was reduced upon the subsequent hydrogen annealing to a trivalent state ($\delta^{**} = -12.3 \pm 0.2 \text{ mm s}^{-1}$, $e^2qQ_{5/2}^{**} = 17.7 \pm 1.1 \text{ mm s}^{-1}$, $\Gamma^{**} = 2.8 \pm 0.2 \text{ mm s}^{-1}$, and $A^{**} = 78\%$). The virtual concentration of Sb^{3+} ions, whose spectral parameters are typical of cations possessing a lone pair E, reflecting the hybridization of their 5s and 5p electronic orbitals,^{8–10} in this sample amounted to nearly 0.5 at%.[†] The photocatalytic measurements revealed a significant decrease in the activity of Sb^{3+} -doped TiO_2 ($k_{\text{Sb}^{3+}}/k_0 = 0.56$), as compared to that observed in the presence of surface-located Sn^{4+} ions creating no V_{O} (material 3, $k_{\text{Sn}^{4+}}/k_0 = 1.16$). However, the slowing of the kinetics induced by Sb^{3+} ions is obviously much weaker than that observed in the presence of 0.6 at% Fe^{3+} ($k_{\text{Fe}^{3+}}/k_0 = 0.13$), the trivalent dopant having no E. These results allowed us to suggest that the moving of the negative charge density of Sb^{3+} lone pair E towards the nearest vacancy V_{O} diminishes its efficiency as an (e^-, h^+) recombination center.

This work was supported by the Russian Foundation for Basic Research (grant no. 19-03-00061).

Online Supplementary Materials

Supplementary data associated with this article can be found in the online version at doi: 10.1016/j.mencom.2021.07.045.

References

- R. A. Astashkin, P. B. Fabritchnyi, M. I. Afanasov, M. V. Korolenko, A. Wattiaux, S. Bordère, C. Labrugère and C. Delmas, *Solid State Sci.*, 2013, **25**, 143.
- H. M. Yadav, T. V. Kolekar, A. S. Barge, N. D. Thorat, S. D. Dolekar, B. M. Kim, B. J. Kim and J. S. Kim, *J. Mater. Sci.: Mater. Electron.*, 2016, **27**, 526.
- S. Ould-Chikh, O. Proux, P. Afanasiev, L. Khrouz, M. N. Hedhili, D. H. Anjum, M. Harb, C. Geantet, J.-M. Basset and E. Puzenat, *ChemSusChem*, 2014, **7**, 1361.
- T. Ikeda, T. Nomoto, K. Eda, Y. Mizutani, H. Kato, A. Kudo and H. Onishi, *J. Phys. Chem. C*, 2008, **112**, 1167.
- A. Di Paola, S. Ikeda, G. Marci, B. Ohtani and L. Palmisano, *Int. J. Photoenergy*, 2001, **3**, 171.
- M. V. Korolenko, P. B. Fabritchnyi and M. I. Afanasov, *Mendelev Comm.*, 2020, **30**, 383.
- M. V. Korolenko, P. B. Fabritchnyi, M. I. Afanasov and C. Labrugère, *Bull. Russ. Acad. Sci.: Phys.*, 2015, **79**, 1055 (*Izv. Akad. Nauk, Ser. Fiz.*, 2015, 1185).
- G. G. Long, J. G. Stevens and L. H. Bowen, *Inorg. Nucl. Chem. Lett.*, 1969, **5**, 799.
- P. E. Lippens, *Solid State Commun.*, 2000, **113**, 399.
- K. Tolborg, C. Gatti and B. B. Iversen, *IUCrJ*, 2020, **7**, 480.

Received: 12th March 2021; Com. 21/6488

[†] Taking into account that the surface-located Sb^{3+} ions may exhibit a somewhat lower value of the recoil-free fraction f at 100 K than that of the bulk-located Sb^{5+} ions, the spectral contribution of the former ions presumably provides an underestimated value of their abundance.