

Enthalpy of sublimation of C₆₀F₃₆

Olga V. Boltalina,^{*a} Vitaliy Yu. Markov,^a Andrey Ya. Borschevskiy,^a Lev N. Sidorov^a and Arkadij Popovich^b

^a Department of Chemistry, M. V. Lomonosov Moscow State University, 119899 Moscow, Russian Federation.

Fax: + 7 095 932 4688

^b J. Stefan Institute, SLO-61111 Ljubljana, Slovenia.

The Knudsen cell mass spectrometry method has been applied in order to obtain the enthalpies of sublimation of C₆₀F₃₆.

The chemistry of fullerenes is one of the most intensively developing fields in fullerene science. Among the fullerene derivatives fluorinated ones are of special interest because of their high thermal stability and unique oxidizing and fluorinating properties.¹ There have been scarcely any data published on the thermodynamic properties of the fluorofullerenes except for a few studies of the gas phase reactions involving some fluorofullerene molecules² and anions of difluorinated fullerenes.³ So far, no data on thermodynamic functions in the condensed matter phase have been obtained — mainly due to the difficulty of controlling the fluorination process and isolating pure products from the mixture, although the selective synthesis of C₆₀F₄₈ has been reported⁴ and the preparation of C₆₀F₃₆ was recently successfully performed by our group.⁵

We report here the first experimental determination of the enthalpy of sublimation of C₆₀F₃₆.

A magnetic sector MI1201 (Russia) mass spectrometer combined with a high temperature ion source was used in our thermodynamic studies.⁶ The C₆₀F₃₆ sample was prepared by the solid phase reaction of C₆₀ with MnF₃ (details are described in our earlier paper⁵). The composition of the sample according to chemical elemental analysis corresponds to C:F = 60:36. A weighed amount (5.25 mg) was then placed into the nickel effusion cell. The cell was resistively heated and the temperature was measured with a Pt/PtRh thermocouple. Electrons of energy 70 eV were used to ionize the molecular beam evaporating from the cell.

The electron impact mass spectrum obtained at 425 K is presented in Figure 1. The peaks corresponding to 1420, 1404, 1382, 1366, 1335 and 702 amu were identified in the spectra and they were assigned to the ions C₆₀F₃₆O⁺, C₆₀F⁺³⁶, C₆₀F₃₄O⁺, C₆₀F⁺³⁴ and C₅₉F⁺³³. The signal at 1404 corresponding to C₆₀F⁺³⁶ was the predominant peak in the available temperature range.

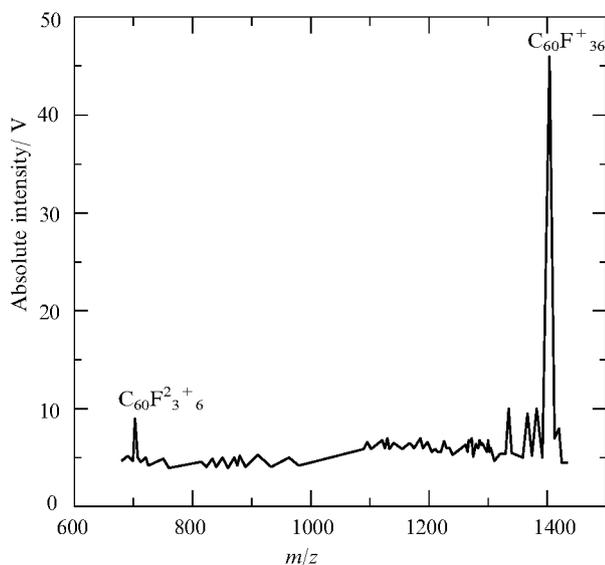


Figure 1 Electron impact mass spectrum at $T = 425$ K in the mass range 690–1430 amu.

To study the molecular presursors of the recorded ions we analysed the mass spectra at different electron energies on a VG double focusing mass spectrometer. Mass spectra obtained at 70 and 12 eV electron energy are shown in Figure 2.

Electron impact ionization is almost unfailingly accompanied by fragmentation of the molecules. One can see from the mass spectra in Figures 2 (a) and (b) that the intensity corresponding to C₅₉F⁺³³ practically vanishes at lower electron energies while C₆₀F⁺³⁶ and C₆₀F⁺³⁴ peaks remain in the spectrum. The CF₃ loss from C₆₀F₃₆ gives the most intensive fragment which agrees with earlier collision induced dissociation (CID) experiments performed on highly fluorinated fullerene species.⁷ The discrepancy of the ion distributions in the spectra shown in Figures 1 and 2 are most probably due to the interaction of the sample with the glass

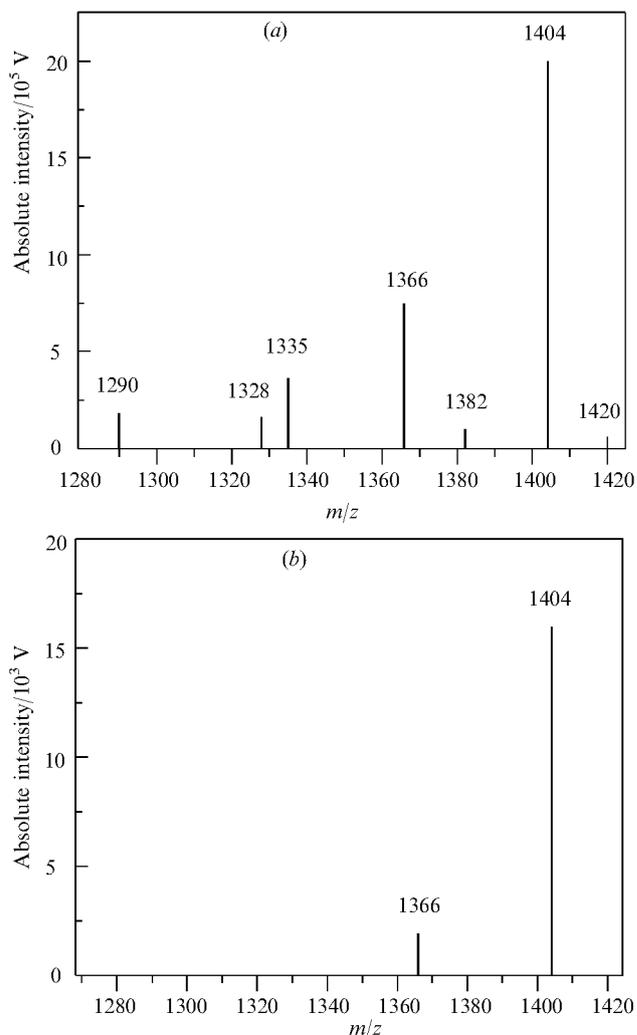


Figure 2 Electron impact mass spectra at different electron energies: (a) 70 eV, (b) 12 eV (mass range 1280–1430 amu).

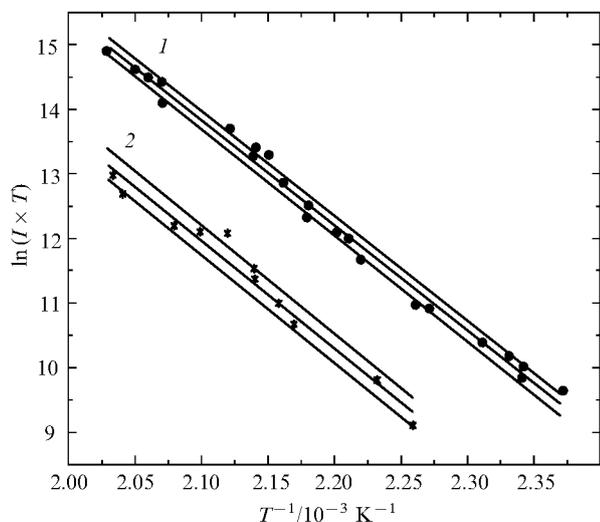


Figure 3 Plot of $\ln(I \times T)$ versus $1/T$ for $C_{60}F_{36}^{+36}$ (first series) (1) and $C_{60}F_{34}O^{+}$ (2). Experimental points, regression lines and confidence bands are presented.

capillary which leads to the partial decomposition of $C_{60}F_{36}$.

Thus small amounts of by-products such as $C_{60}F_{34}$, $C_{60}F_{34}O$ and $C_{60}F_{36}O$ are, apparently, present in the $C_{60}F_{36}$ sample prepared. Attempts to further purify the sample by resublimation or changing the synthesis conditions did not markedly change its composition.⁵ High performance liquid chromatography (HPLC) separation may be an alternative way for the future isolation of pure compounds provided one finds the proper solvent and suitable experimental conditions. One can not exclude the possibility of degradation of $C_{60}F_{36}$ under heating or its reaction with the walls of the cell or glass capillary in the mass spectrometer.

Two series of the temperature dependence of $C_{60}F_{36}^{+36}$ ion were obtained in the temperature range 422–525 K. The enthalpy of sublimation was derived from the equation:

$$\ln(I_{ij}T) = -\langle \Delta_s H_T^0 \rangle_j / RT + C \quad (1)$$

where I_{ij} is the ion current of an ion i formed from the molecule j ; $\langle \Delta_s H_T^0 \rangle_j$ is the enthalpy of sublimation of compound j (as noted above it is averaged in our case), T is the absolute temperature, R is the universal gas constant, C is a constant depending on the ionization cross-section, sensitivity coefficient and mole fraction in the sample. The enthalpy of sublimation can be calculated from the slope of a plot of $\ln(I_{ij}T)$ versus $1/T$.⁶

The slope was derived *via* a least squares treatment of the data. The experimental data obtained for $C_{60}F_{36}^{+36}$ (one series) and the impurity $C_{60}F_{34}O^{+}$ are plotted in Figure 3 as a function of $\ln(I \times T)$ versus $1/T$.

As shown previously in a ^{19}F NMR study⁵ the $C_{60}F_{36}$ sample represents a mixture of four isomers and nothing is known of the $C_{60}F_{34}O$ isomers. Therefore the sublimation enthalpy obtained in this work is defined as the value averaged over all the existing isomers:

$$\langle \Delta_s H_T^0 \rangle = \sum y_i (\Delta_s H_T^0)_i, \quad (2)$$

where y_i is the mole fraction of the i -th isomer and $(\Delta_s H_T^0)_i$ is the enthalpy of sublimation of the i -th isomer. We assume that y_i does not depend on temperature in the available temperature range.

The sublimation enthalpy values obtained for $C_{60}F_{36}$ in two series agree within experimental error and were averaged to further remove uncertainties. The recommended value for the

enthalpy of sublimation of $C_{60}F_{36}$ is as follows:

$$\langle \Delta_s H_T^0 \{C_{60}F_{36}\} \rangle = (134 \pm 6) \text{ kJ mol}^{-1}$$

We also obtained the partial enthalpy of sublimation of $C_{60}F_{34}O$:

$$\langle \Delta_s H_T^0 \{C_{60}F_{34}O\} \rangle_m = (136 \pm 14) \text{ kJ mol}^{-1}$$

Assuming the formation of an ideal solution the obtained partial sublimation enthalpy of $C_{60}F_{34}O$ is an estimation of the sublimation enthalpy of this compound.

As pointed out above, nothing has been known to date concerning the evaporation behaviour of fluorofullerenes and no data has been published on the thermodynamic parameters of other fullerene derivatives in the solid phase. Thus it is interesting to compare the obtained data with the sublimation enthalpy of the pristine fullerene C_{60} which is, according to the latest result by Gigli *et al.*,⁸ $\approx 50 \text{ kJ mol}^{-1}$ higher than that of $C_{60}F_{36}$ [$\Delta_s H_T^0(C_{60}F_{36}, 298 \text{ K}) = (181 \pm 2) \text{ kJ mol}^{-1}$].⁸

In summary, the evaporation study of $C_{60}F_{36}$ demonstrated that it is highly thermally stable and that it sublimates congruently without decomposition at lower temperatures than that of pristine C_{60} .

We are grateful to the Russian Foundation for Basic Research (grant no. 95-03-0979a), Russian Research Program 'Fullerenes and Atomic Clusters' (grant no. 94019) and the Royal Society for financial support of this work. We thank Dr. A. G. Buyanovskaya and I. G. Barakovskaya for providing elemental analysis data. O.V.B. thanks Dr. R. Taylor, Sussex University, UK, for collaboration.

References

- 1 A. A. Gakh, A. A. Tuinman, J. L. Adcock and R. N. Compton, *Tetrahedron Lett.*, 1993, **34**, 7167.
- 2 I. N. Malkerova, D. V. Sevast'yanov, A. S. Alikhanyan, S. P. Ionov and N. G. Spitsyna, *Dokl. Akad. Nauk, Ser. Khim.*, 1995, **342**, 630 [*Dokl. Chem. (Engl. Transl.)*, 1995, **342**, 142].
- 3 O. V. Boltalina, L. N. Sidorov, E. V. Sukhanova and I. D. Sorokin, *Chem. Phys. Lett.*, 1994, **230**, 567.
- 4 A. A. Gakh, A. A. Tuinman and J. L. Adcock, *J. Am. Chem. Soc.*, 1994, **116**, 819.
- 5 O. V. Boltalina, A. Ya. Borschevskii, L. N. Sidorov, J. M. Street and R. Taylor, *J. Chem. Soc., Chem. Commun.*, in press.
- 6 L. N. Sidorov, M. V. Korobov and L. V. Zhuravleva, *Mass-spektral'nye termodinamicheskie issledovaniya, (Mass Spectral Thermodynamic Studies)*, Izd. MGU, Moscow, 1985 (in Russian).
- 7 A. A. Tuinman, P. Mukherjee, J. L. Adcock, R. L. Hettich and R. N. Compton, *J. Phys. Chem.*, 1992, **96**, 7584.
- 8 V. Piacente, G. Gigli, P. Scaidala and A. Giustino, *J. Phys. Chem.*, 1995, **99**, 14052.

Received: Moscow, 8th April 1996

Cambridge, 20th May 1996; Com. 6/02657E